



# Rynite® RE15022 NC010

## THERMOPLASTIC POLYESTER RESIN

Common features of Rynite® thermoplastic polyester include mechanical and physical properties such as excellent balance of strength and stiffness, dimensional stability, creep resistance, heat resistance, high surface gloss and good inherent electrical properties at elevated temperature. It can be processed over a broad temperature range and has excellent flow properties.

Rynite® thermoplastic polyester resins are typically used in demanding applications in the automotive, electrical and electronics, appliances where they successfully replace metals and thermosets, as well as other thermoplastic polymers.

Rynite® RE15022 NC010 is a 36% glass reinforced modified polyethylene terephthalate resin developed for applications that need high burst strength and fast cycle performance.

### Product information

Resin Identification	PET-GF36	ISO 1043
Part Marking Code	>PET-GF36<	ISO 11469

### Rheological properties

Moulding shrinkage, parallel	0.1 %	ISO 294-4, 2577
Moulding shrinkage, normal	1.0 %	ISO 294-4, 2577
Mold Shrinkage, Flow, 3.2mm (0.125in)	0.13 %	
Mold Shrinkage, Transverse, 3.2mm (0.125in)	0.99 %	

### Typical mechanical properties

Tensile Modulus	14000 MPa	ISO 527-1/-2
Stress at break	200 MPa	ISO 527-1/-2
Strain at break	2.4 %	ISO 527-1/-2
Charpy impact strength, 23°C	70 kJ/m <sup>2</sup>	ISO 179/1eU
Charpy notched impact strength, 23°C	11 kJ/m <sup>2</sup>	ISO 179/1eA
Charpy notched impact strength, -30°C	11 kJ/m <sup>2</sup>	ISO 179/1eA
Charpy notched impact strength, -40°C	11 kJ/m <sup>2</sup>	ISO 179/1eA
Poisson's ratio	0.33 -	

### Thermal properties

Melting temperature, 10°C/min	247 °C	ISO 11357-1/-3
Temp. of deflection under load, 1.8 MPa	235 °C	ISO 75-1/-2
Temp. of deflection under load, 0.45 MPa	245 °C	ISO 75-1/-2
Coeff. of linear therm. expansion, parallel	20 E-6/K	ISO 11359-1/-2
Coeff. of linear therm. expansion, normal	70 E-6/K	ISO 11359-1/-2



# Rynite<sup>®</sup> RE15022 NC010

THERMOPLASTIC POLYESTER RESIN

## Flammability

FMVSS Class	B -	ISO 3795 (FMVSS 302)
Burning rate, Thickness 1 mm	<80 mm/min	ISO 3795 (FMVSS 302)

## Other properties

Density	1650 kg/m <sup>3</sup>	ISO 1183
---------	------------------------	----------

## Injection

Drying Recommended	yes
Drying Temperature	120 °C
Drying Time, Dehumidified Dryer	4 - 6 h
Processing Moisture Content	≤0.01 <sup>[1]</sup> %
Melt Temperature Optimum	285 °C
Min. melt temperature	280 °C
Max. melt temperature	300 °C
Max. screw tangential speed	0.2 m/s
Mold Temperature Optimum	140 °C
Min. mould temperature	120 °C
Max. mould temperature	140 <sup>[2]</sup> °C
Hold pressure range	≥80 MPa
Hold pressure time	4 s/mm
Back pressure	As low as possible MPa
Ejection temperature	170 °C

[1]: At levels above 0.01%, strength and toughness will decrease, even though parts may not exhibit surface defects.


[2]: (6mm - 1mm thickness)



# Rynite<sup>®</sup> RE15022 NC010

THERMOPLASTIC POLYESTER RESIN

Tensile Fatigue, 10Hz, R=0.1 @ mm

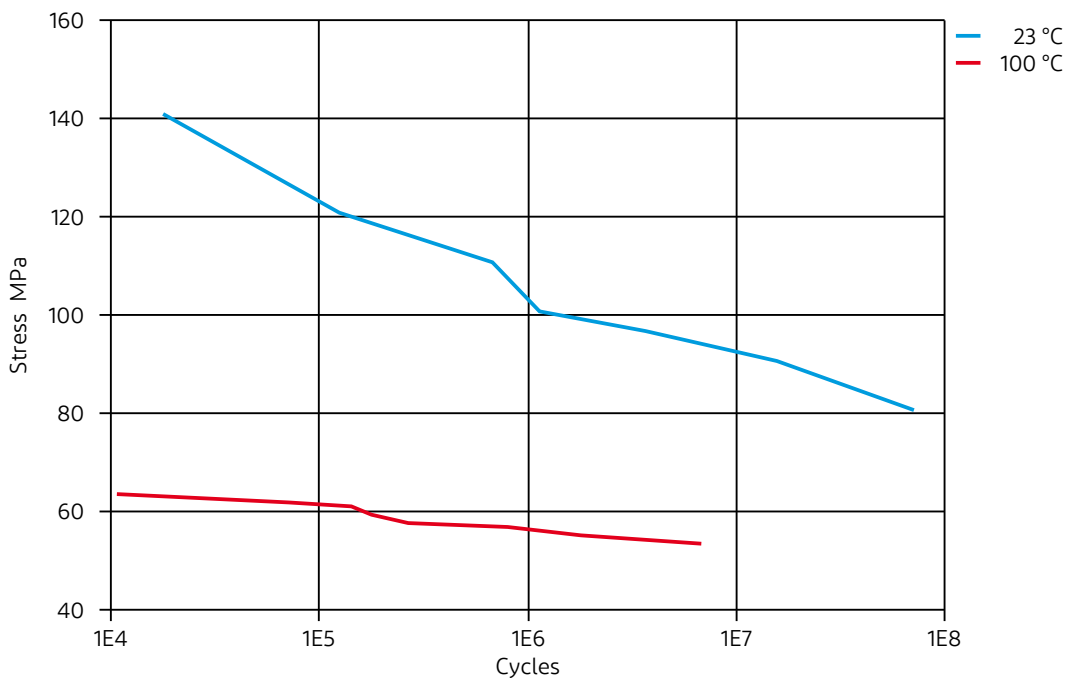

The information set forth herein is furnished free of charge, is based on technical data that DuPont believes to be reliable, and represents typical values that fall within the normal range of properties. This information relates only to the specific material designated and may not be valid for such material used in combination with other materials or in other processes. It is intended for use by persons having technical skill, at their own discretion and risk. This information should not be used to establish specification limits nor used alone as the basis of design. Handling precaution information is given with the understanding that those using it will satisfy themselves that their particular conditions of use present no health or safety hazards and comply with applicable law. Since conditions of product use and disposal are outside our control, we make no warranties, express or implied, and assume no liability in connection with any use of this information. As with any product, evaluation under end-use conditions prior to specification is essential. Nothing herein is to be taken as a license to operate or a recommendation to infringe on patents.

CAUTION: Do not use DuPont materials in medical applications involving implantation in the human body or contact with internal body fluids or tissues unless the material has been provided from DuPont under a written contract or other acknowledgement that is consistent with the DuPont policy regarding medical applications and expressly acknowledges the contemplated use. For further information, please contact your DuPont representative.

DuPont's sole warranty is that our products will meet our standard sales specifications in effect at the time of shipment. Your exclusive remedy for breach of such warranty is limited to refund of purchase price or replacement of any product shown to be other than as warranted. TO THE FULLEST EXTENT PERMITTED BY APPLICABLE LAW, DUPONT SPECIFICALLY DISCLAIMS ANY OTHER EXPRESS OR IMPLIED WARRANTY OF FITNESS FOR A PARTICULAR PURPOSE, MERCHANTABILITY, OR NON-INFRINGEMENT. DUPONT DISCLAIMS LIABILITY FOR ANY SPECIAL, INCIDENTAL, OR CONSEQUENTIAL DAMAGES.